

High Pressure Structure and Decomposition of MoS₂

Oto Kohulák,¹ Roman Martoňák,^{1,*} and Erio Tosatti^{2,3}

¹*Department of Experimental Physics, Comenius University,*

Mlynská Dolina F2, 842 48 Bratislava, Slovakia

²*International School for Advanced Studies (SISSA) and CNR-IOM Democritos,*

Via Bonomea 265, I-34136 Trieste, Italy

³*The Abdus Salam International Centre for Theoretical Physics (ICTP),*

Strada Costiera 11, I-34151 Trieste, Italy

(Dated: December 15, 2014)

Abstract

The high pressure structural and electronic evolution of bulk MoS₂, an important transition metal layered dichalcogenide, is currently under active investigation. Recent theoretical and experimental work predicted and verified a $2H_c \rightarrow 2H_a$ layer sliding structural transition at 20 GPa and a band overlap semiconductor-semimetal transition in the same pressure range. The $2H_a$ structure is known to persist up to pressure of 81 GPa but properties at higher pressures remain experimentally unknown. Here we predict, with a reliable first-principles evolutionary search, that major structural transformations should take place in equilibrium at higher pressures near 130-140 GPa. The main motif is a decomposition into MoS + S, also heralded in a small bimolecular cell by the appearance of a metastable non-layered metallic MoS₂ structure with space group $P4/mmm$. Unlike semimetallic $2H_a$ -MoS₂, both this phase and sulphur in the fully phase separated system are fully metallic and superconducting with higher critical temperatures than alkali-intercalated MoS₂.

PACS numbers: 61.50.Ks, 71.30.+h, 72.80.Ga, 74.10.+v

MoS₂ is layered semiconductor, long known as a solid lubricant,¹ of more recent importance for its applications and, in exfoliated form, as an electronic material.^{2,3} It is also relevant for superconductivity as a parent material that can be metallized by alkali doping⁴ or by surface field doping^{5,6}. In pursuit of superconductivity, it is currently studied at ultra high pressures, where it was shown theoretically⁷ and experimentally⁸ to undergo, besides a layer sliding structural transition at 20 GPa from the 2H_c to the 2H_a structure, a band overlap metallization at 30-40 GPa⁷⁻⁹. The 2H_a structure was experimentally shown to persist at least up to 81 GPa [Ref.⁸] but the further evolution of structure and electronic properties remain experimentally unclear at higher pressures. Were the 2H_a structure to persist further in that regime, one might anticipate a relatively weak metallicity with modest superconducting tendencies.^{7,10} There could, however, be other structures coming up at ultra-high pressures, possibly with a stronger metallicity and superconductivity. Alternatively, the stability of MoS₂ as a compound might be altogether lost giving rise, under sufficient pressure, to decomposition and phase separation into products with different stoichiometries and different properties.

We present here the results of first principle simulations which predict that at thermodynamic equilibrium 2H_a-MoS₂ should become unstable against both possibilities, phase transformation or decomposition, when pressure reaches values between 130 and 140 GPa. State-of-the-art density functional theory (DFT) calculations, particularly accurate at higher pressure, can reliably explore the equilibrium phase diagram of MoS₂ in this regime once they are coupled with a suitable structure search algorithm.

Using the genetic search algorithm as implemented in the Xtalopt package¹¹ we performed a search of the lowest enthalpy T=0 crystal structure of MoS₂ at 80, 120 and 150 GPa using supercells with 6, 9 and 12 atoms, corresponding to 2, 3 and 4 formula units. Using the PBE¹² XC potential, we employed for the 6 and 9 atoms/cell the Quantum Espresso¹³ code with a PW cutoff of 60 Ry and a 4x4x4 k-point grid, and for the 12 atoms/cell the VASP code¹⁴ with 450 eV cutoff and automatic k-point mesh generation of length 30¹⁷.

Results of this extensive and unprejudiced high pressure structural search recover and reproduce first of all the well-known 2H_a, 2H_b, 2H_c and 3R layered structures. As was found in previous work, 2H_a has the lowest enthalpy among them in the selected pressure range⁷. However, a new structure was also found with 6 atoms/cell and space group *P*4/*mmm* (Fig.1). As shown by the calculated enthalpies in Fig.2 the tetragonal *P*4/*mmm* competes

strongly with $2H_a$ at sufficiently high pressure where, with a strongly first order phase transition involving a volume drop of about 5 % it overcomes the $2H_a$ structure at 138 GPa. Fully relaxing and optimizing the $P4/mmm$ structure at 150 GPa, we refined at this pressure its structural and electronic properties. The new structure has a bimolecular cell like $2H_a$, but unlike it is not layered. The $P4/mmm$ unit cell is tetragonal with lattice parameters $a = 2.701 \text{ \AA}$, $c = 7.933 \text{ \AA}$. It contains two Mo atoms, each surrounded by eight S atoms in a CsCl local coordination, plus one S atom in an S-atom bcc cage. The band structure and electronic density of states (Figs. 3 and 4) show a strongly metallic character, as opposed to the $2H_a$ structure which even at this pressure is only weakly metallic⁷. The calculated phonon dispersion (Fig.5) which we obtained using QE shows that at 150 GPa the $P4/mmm$ structure is locally stable. Based on this electronic and phonon structure we calculate the electron-phonon coupling parameter and find $\lambda \sim 0.75$, much larger than that calculated for the $2H_a$ structure^{7,10}, suggesting a superconducting temperature T_c of about 15 K obtained assuming $\mu^* = 0.1$. Therefore a transformation $2H_a \rightarrow P4/mmm$ could in principle lead to the abrupt onset of superconductivity at low temperatures and high pressures.

Further calculations, however, suggest that a structural transformation from $2H_a \rightarrow P4/mmm$ is not the likeliest equilibrium occurrence in MoS_2 at high pressure. The $P4/mmm$ structure actually consists of adjacent nanosized elemental sulphur and MoS crystals. That suggests another possible scenario, namely $\text{MoS} + \text{S}$ chemical decomposition. Because MoS is not a well known phase, additional calculations are needed in order to confirm or deny that kind of high pressure transformation route.

We carried out a genetic algorithm search on MoS, and indeed found a stable structure of MoS at 120 GPa, endowed precisely with the CsCl structure, which is metallic. The structure of elemental sulphur in this pressure range is known to be the phase IV, body-centered monoclinic with an incommensurate modulation¹⁵. Neglecting the modulation we calculated the enthalpy curve corresponding to the $\text{MoS} + \text{S}$ decomposition enthalpy which is shown in Fig.2. It should be noted that inclusion of modulation could at most slightly decrease the decomposition pressure, but will not increase it. Thus, decomposition with phase separation of $2H_a \rightarrow \text{MoS} + \text{S}$ is predicted to take place at or below 135 GPa, preempting the structural transformation to the $P4/mmm$ phase. Decomposition of $2H_a$ therefore represents the predicted thermodynamic evolution under pressure. Since elemental sulphur in phase IV is known to superconduct above 93 GPa¹⁶ with $T_c > 10 \text{ K}$, the decomposition scenario should

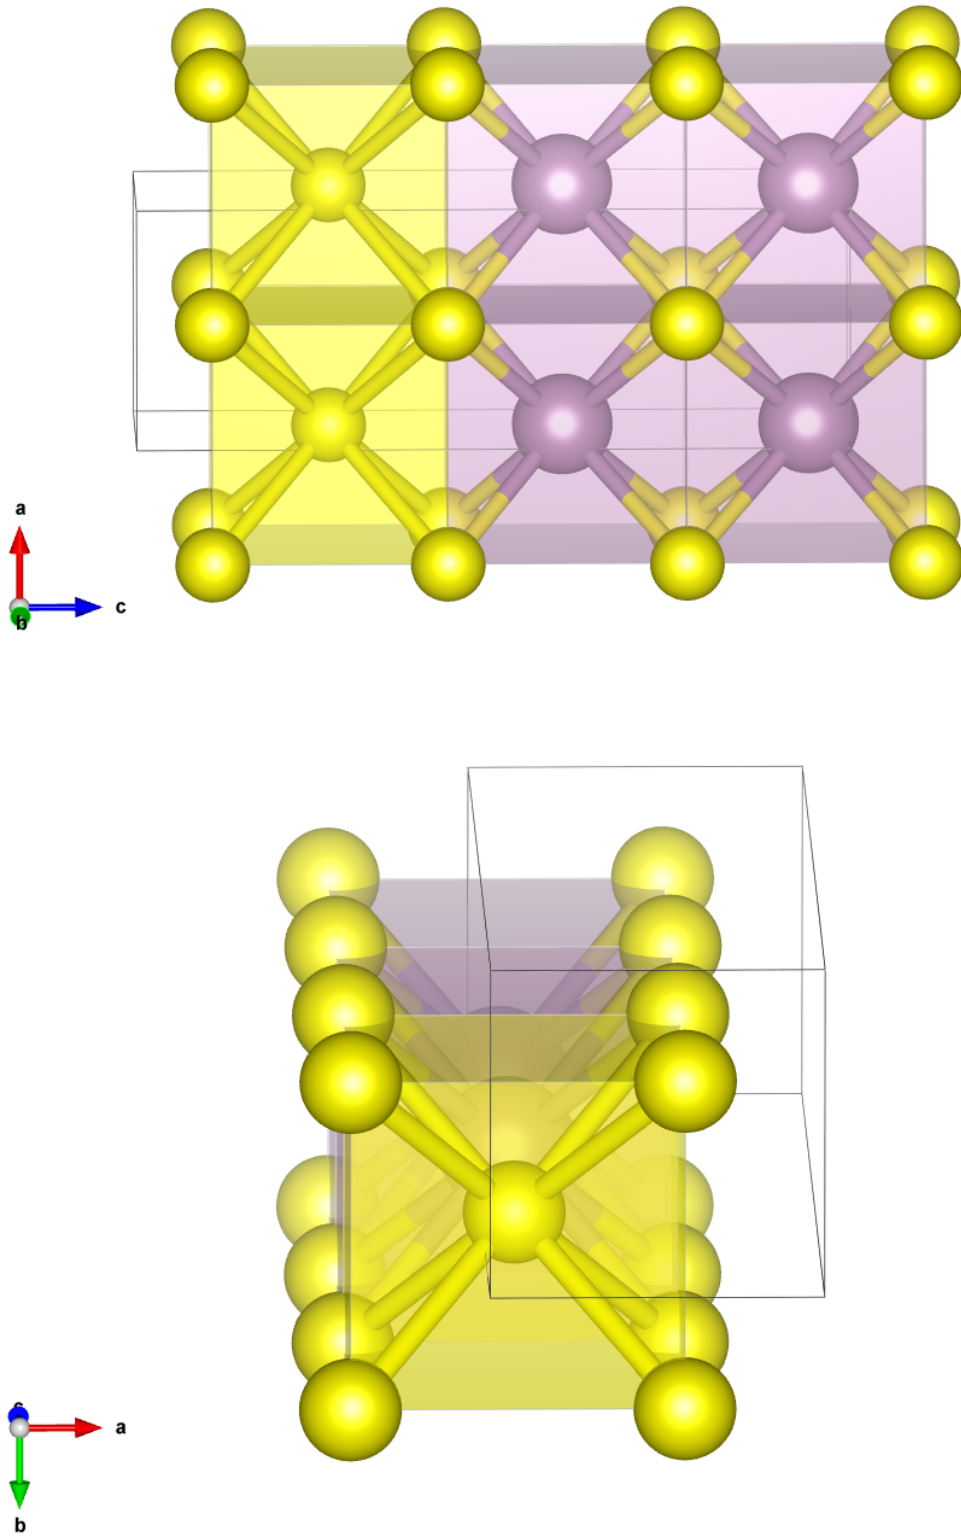


FIG. 1: Structure of the $P4/mmm$ phase. On the upper panel 2 unit cells are shown.

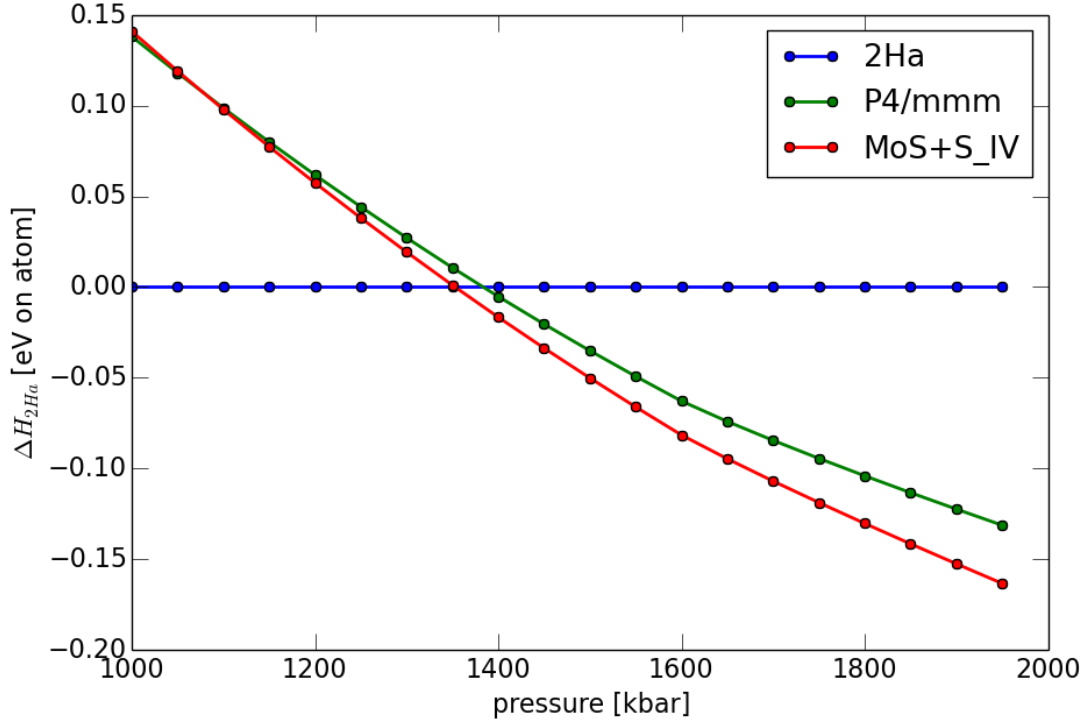


FIG. 2: Evolution of enthalpy with increasing pressure for various phases. The $2H_a$ structure is taken as reference. Enthalpies were calculated with Quantum Espresso, using k-points mesh of $12 \times 12 \times 4$ for the $2H_a$ and $P4/mmm$, $12 \times 12 \times 12$ for MoS and $13 \times 13 \times 13$ for SIV.

lead to the abrupt onset of superconductivity in the S component.

Because the enthalpies of $P4/mmm$ and of MoS + S are so very close, a structural transformation to the metastable $P4/mmm$ phase, or some other similar phase with a larger unit cell, cannot be ruled out and might take place experimentally, especially if decomposition was protected by a high barrier, or simply if the necessary diffusion of phase separated S turned out to be kinetically too slow. Other possibilities might include intermediate routes such as partial decomposition with formation of e.g., filamentary sulphur. Alternatively, MoS₂ might conceivably survive in a metastable $2H_a$ structure even above 138 GPa, owing to the presumably slow kinetics of experimental phase transformations and separations. Whether the predicted equilibrium transformations will take place in ultra-high pressure MoS₂ and if so in what form will depend exquisitely on these kinetic factors, and can only be established experimentally.

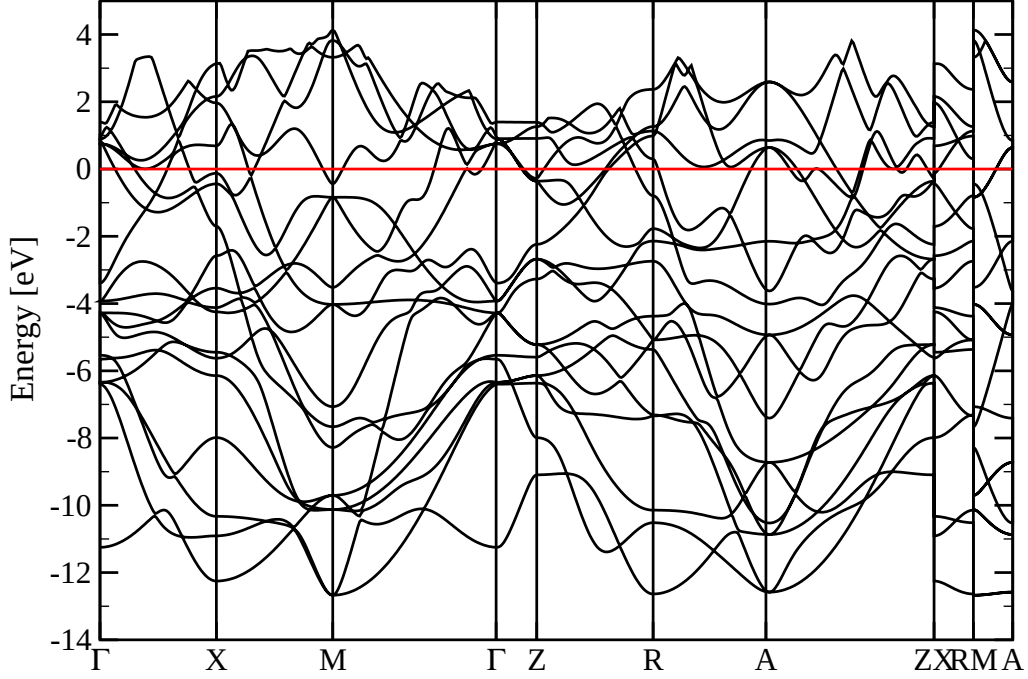


FIG. 3: Band structure for $P4/mmm$ calculated from QE at 150 GPa. The Fermi level is shown with red line.

Acknowledgments

O.K. and R.M. were supported by the Slovak Research Development Agency under Contract APVV-0108-11 and R.M. was also supported by the contract APVV-0558-10. We also acknowledge support from the project implementation 26220220004 within the Research & Development Operational Programme funded by the ERDF. Part of the calculations was performed in the Computing Centre of the Slovak Academy of Sciences using the supercomputing infrastructure acquired in project ITMS 26230120002 and 26210120002 (Slovak infrastructure for high-performance computing) supported by the Research & Development Operational Programme funded by the ERDF. Work in Trieste was partly sponsored by EU-Japan Project LEMSUPER, by Sinergia Contract CRSII2₁36287/1, and by ERC Advanced Grant 320796 - MODPHYSFRICT. We are especially grateful to G. Profeta, A. Sanna for

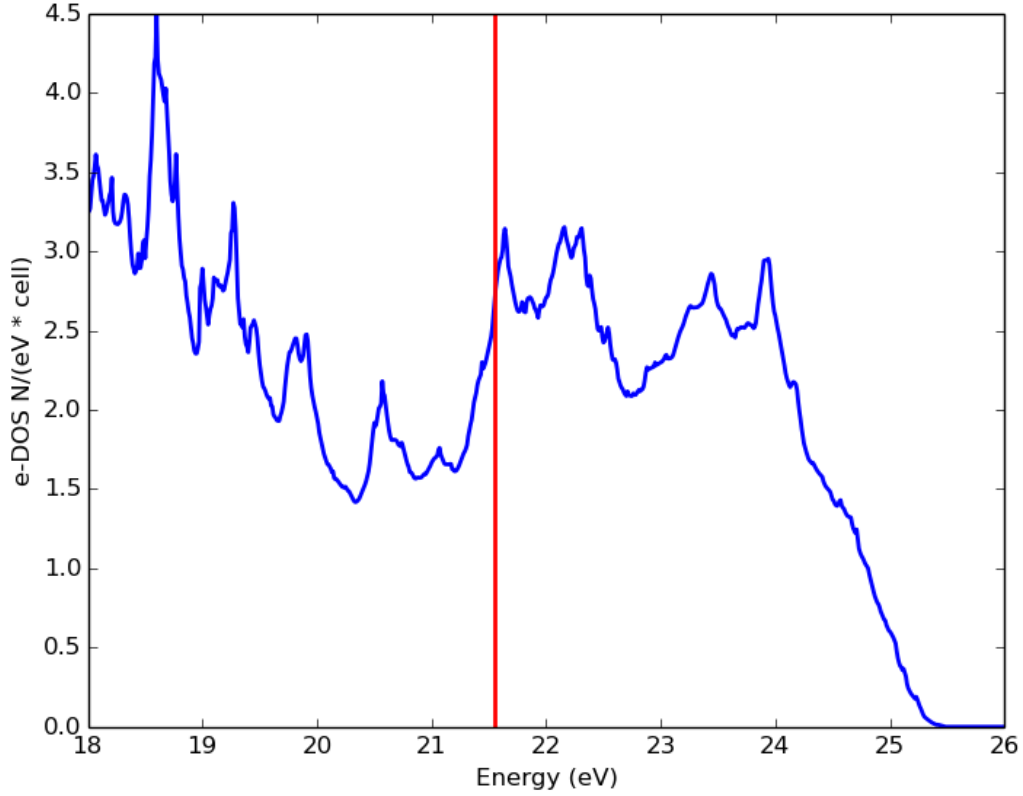


FIG. 4: e-DoS for the $P4/mmm$ structure calculated from QE at 150 GPa. The Fermi level is shown with red line.

information on their unpublished calculations, and to Z. Chi, T. Kagayama, Y. Iwasa and K. Shimizu for discussion and information on experimental aspects.

* Electronic address: martonak@fmph.uniba.sk

¹ M. Dallavalle, N. Sndig, and F. Zerbetto, *Langmuir* **28**, 7393 (2012).

² K. F. Mak, C. Lee, J. Hone, J. Shan, and T. F. Heinz, *Phys. Rev. Lett.* **105**, 136805 (2010).

³ B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti, and A. Kis, *Nat. Nano.* **6**, 147 (2011).

⁴ R. B. Somoano, V. Hadek, and A. Rembaum, *The Journal of Chemical Physics* **58**, 697 (1973).

⁵ K. Taniguchi, A. Matsumoto, H. Shimotani, and H. Takagi, *Appl. Phys. Lett.* **101**, 042603 (2012).

⁶ J. T. Ye, Y. J. Zhang, R. Akashi, M. S. Bahramy, R. Arita, and Y. Iwasa, *Science* **338**, 1193

$P4/mmm$ MoS₂ 150 GPa

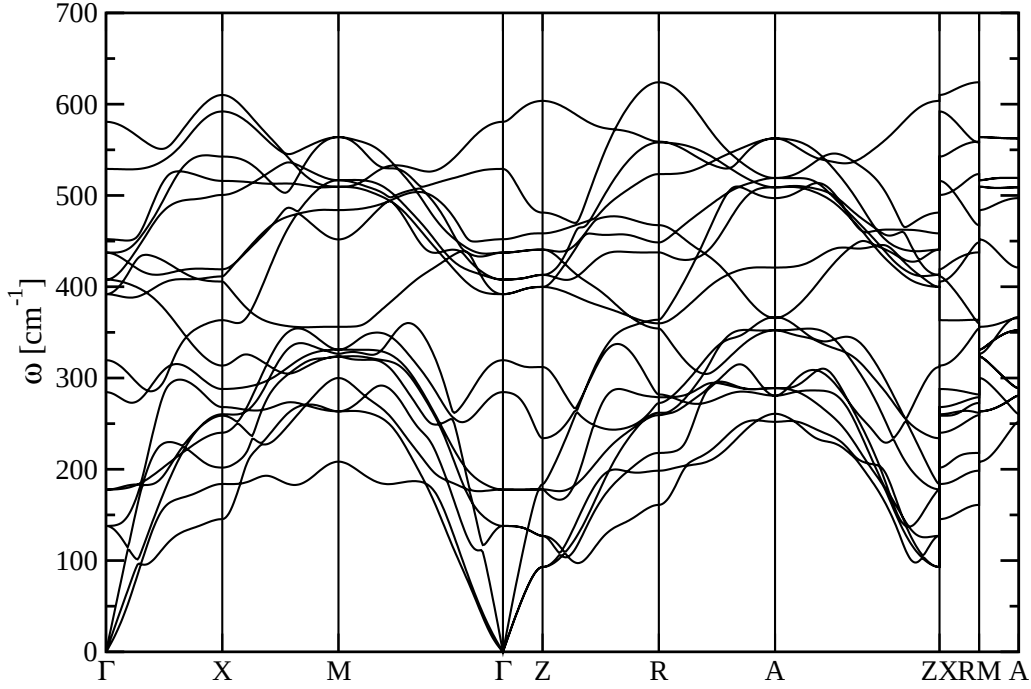


FIG. 5: Phonon dispersion in the $P4/mmm$ structure at 150 GPa.

(2012).

- ⁷ L. Hromadová, R. Martoňák, and E. Tosatti, Phys. Rev. B **87**, 144105 (2013).
- ⁸ Z.-H. Chi, X.-M. Zhao, H. Zhang, A. F. Goncharov, S. S. Lobanov, T. Kagayama, M. Sakata, and X.-J. Chen, Phys. Rev. Lett. **113**, 036802 (2014), URL <http://link.aps.org/doi/10.1103/PhysRevLett.113.036802>.
- ⁹ A. Nayak, S. Bhattacharyya, J. Zhu, J. Liu, X. Wu, T. Pandey, C. Jin, A. Singh, D. Akinwande, and J. Lin, Nature Communications **5**, 3731 (2014).
- ¹⁰ A. Sanna and G. Profeta, unpublished.
- ¹¹ D. C. Lonie and E. Zurek, Computer Physics Communications **182**, 372 (2011).
- ¹² J. P. Perdew, K. Burke, and M. Ernzerhof, Phys. Rev. Lett. **77**, 3865–3868 (1996).
- ¹³ P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, et al., Journal of Physics: Condensed Matter **21**, 395502

(19pp) (2009), URL <http://www.quantum-espresso.org>.

¹⁴ G. Kresse and J. Furthmüller, Phys. Rev. B **54**, 11169 (1996).

¹⁵ O. Degtyareva, E. Gregoryanz, M. Somayazulu, H.-k. Mao, and R. J. Hemley, Phys. Rev. B **71**, 214104 (2005), URL <http://link.aps.org/doi/10.1103/PhysRevB.71.214104>.

¹⁶ O. Degtyareva, M. V. Magnitskaya, J. Kohanoff, G. Profeta, S. Scandolo, M. Hanfland, M. I. McMahon, and E. Gregoryanz, Phys. Rev. Lett. **99**, 155505 (2007), URL <http://link.aps.org/doi/10.1103/PhysRevLett.99.155505>.

¹⁷ see the VASP manual